

# **SOLSTICE<sup>®</sup>** **LIQUID BLOWING AGENT**

Maximizing Performance  
of Spray Foam Systems  
Formulated with Solstice LBA

---

Quick Reference Guide


---



# Introduction

Honeywell Solstice® Liquid Blowing Agent (LBA), based on hydrofluoro-olefin HFO technology, is an ideal ultra-low global-warming-potential (GWP) replacement for HFC foam blowing agents commonly used in closed-cell spray polyurethane foam (ccSPF) systems. A growing number of companies have already adopted Solstice LBA or are making the switch. Not only does Solstice LBA help their systems comply with current and future regulations, it is providing better performance (insulation, yield, sprayability, etc.) compared to current systems.

To help facilitate that transition, we've assembled this quick reference guide. We offer suggestions intended to help formulators (systems houses) and contractors maximize the performance of their polyol pre-blend formulated with Solstice LBA. When developing a system with Solstice LBA, it is important to consider packaging design, storage, and transportation. Processing conditions and equipment are also important factors. We've provided some troubleshooting tips to help you manage potential challenges that can arise, including the impact of vapor pressure and the possibility of frothing of the polyol blend that can occur when it's exposed to high ambient temperatures or severe agitation.

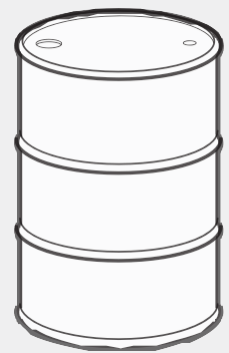

This reference guide is not intended to replace comprehensive technical literature and safety data sheets (SDS) for Solstice LBA that are also available from Honeywell.

## Understanding Contributors to Vapor Pressure and Frothing

Many factors contribute to the vapor pressure of a fluid, viscosity and surface tension of the solution, the solubility of the low boiling material in the solution, and of course, the solution temperature. Polyol blends are typically stored and shipped in 208 liter/55 gallon drums that are sometimes exposed to elevated temperatures in the field. Pressure builds in a closed container, such as a drum, when a solution containing a low boiling material is heated above the boiling point of the material. If the container is opened quickly and the pressure is released, the dissolved gas from the low boiling point liquid is quickly released from the solution and frothing may occur. This is like what happens if a warm bottle of soda is opened quickly.



If a soda bottle is shaken and then opened, liquid soda and bubbles will froth out of the bottle. If the soda bottle is allowed to settle after being shaken, it is far less likely to froth. This is a similar effect that can be seen with polyol blends.

## Proper Shipping and Handling of Material Can Reduce Frothing

This brochure offers guidance on what precautions can be taken to reduce the potential for the polyol blend to froth when a drum is opened in the field. The potential for a fluid to froth is a function of many of the same factors that influence vapor pressure, but frothing and vapor pressure are independent phenomena and not always linked.

Contributing factors include the concentration of the low boiling material, the temperature of the polyol blend relative to the boiling point of the material, the surface tension, the viscosity of the fluid, the uniformity of the polyol blend, and the miscibility of the blowing agent in the polyol blend.

In addition to the properties of the fluid that are addressed with vapor pressure, how the material is handled also plays a significant role in determining whether frothing will occur. Agitation of the polyol blend during shipping or handling, and/or inserting warm drum pumps, can impact the potential for frothing by affecting the miscibility of the “low boiling point liquid” in the polyol blend. By allowing the polyol blend drum to rest after potentially being agitated or shaken during transport, the internal pressure can equilibrate and the sudden release of pressure when opening the drum can be reduced or eliminated.

# Packaging

Choice of packaging when using a polyol pre-blend that includes Solstice LBA, or any foam blowing agent, is an important consideration. As mentioned, drums are commonly used across the spray foam industry for polyol pre-blend, which contains a mixture of polyol, blowing agent, catalyst, surfactant, and other ingredients. Other packaging options – such as cylinders, totes, or larger bulk containers – are also available. Packaging options vary depending on the region.

## Vapor Pressure Management

When selecting polyol pre-blend packaging, vapor pressure management is an important consideration. Factors impacting vapor pressure of a polyol pre-blend are complex. As mentioned, it can be impacted by the boiling point of the blowing agent (Solstice LBA has a boiling point of 19°C/66°F), the amount of blowing agent in the polyol pre-blend, and the temperature of the blend. Other factors that contribute to vapor pressure include the solubility of the blowing agent in the polyol, the presence of other gases or volatile liquids in the pre-blend, including air, and the method used to measure the vapor pressure. It is important to understand these factors and to manage the temperature of the system per the formulator’s guidelines. By doing so, this will help control the internal vapor pressure of the package.

## Packaging Considerations

### Drums 1 2

- Vendors of drums conform to U.S. DOT Hazardous Materials Regulations (49 CFR)
- The UN Performance Packaging concept no longer specifies gauge thickness – only test criteria. A typical drum package might be labeled: 1A1 / Y1.4 / 250 / 04 / USA / BK123. (See page 7)<sup>†</sup>
- Honeywell recommends a minimum service pressure of 22 psi/1.51 Bar/151.7 kPa. Note: While it is recognized that some distortion is likely at this internal pressure, it is unlikely that failure would occur

Note: Consult your drum vendor for design specifications.

<sup>†</sup> Example of typical drum package label: 1A1 / Y1.4 / 250 / 04 / USA / BK123.


#### Where:

UN	=	United Nations (globally accepted)
1	=	Drum
A	=	Steel
1	=	Closed Head (bung)
Y	=	Drum is acceptable for hazmat in packaging group II and III only
1.4	=	Maximum specific gravity of the liquid in the drum
250	=	Hydrostatic test pressure for the drum (250 kPa)
04	=	Year of manufacture
USA	=	Country of authorization
BK123	=	Registered symbol or code of the testing entity

## Factors impacting vapor pressure of a polyol pre-blend are complex.


1

Example of 208 Liter/55 Gallon Drum

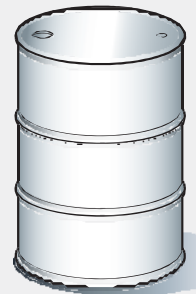

2

Overhead View of Typical Drum

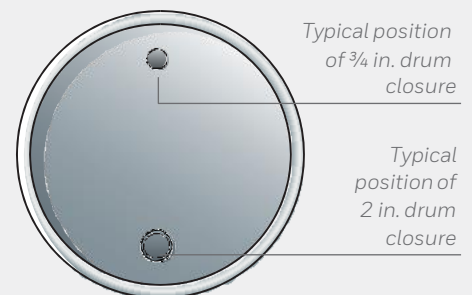

Note: The measurement of drum openings (bung holes) may vary by region, though typically they are similar in size to the openings indicated.

## Packaging Considerations (Continued)

### Solid Drum Closures

In conjunction with drum choice, the matter of pressure management (or pressure relief) and the choice of drum closure is of equal importance.

Solid drum closures are commonly used. When opening a drum using solid drum closures, safety measures should be taken in the event of internal vapor pressure build-up. It is important to work closely with the system formulator to define safe use and handling procedures. Ensure that personnel responsible for handling and opening drums are wearing proper personal protective equipment (PPE) and are well-trained on all safe use and handling procedures.

#### Here are some suggested steps:

1. The smaller drum closure ( $\frac{3}{4}$  in.) **3** should be opened first, slowly and partially to allow relief of any internal pressure
2. Next, this  $\frac{3}{4}$  in. closure can be removed to ensure there is no pressure in the drum
3. With zero pressure confirmed, the larger solid drum closure (2 in.) **4** should also be removed to accommodate a drum pump

### Vented Drum Closures

A variety of vented drum closures are also available for consideration. Safety precautions must also be applied when handling drums with vented drum closures.

- Vented drum closures (2 in.) **5** are used extensively to help ensure that the drum has an internal pressure less than design relief pressure of the closure
- The recommended vented closure is the type that opens at a pre-set pressure (typically 12-15 psi/0.82-1.03 Bar/82.7 – 103.4 kPa) and closes automatically at a pre-set pressure (typically 8 psi/0.55 Bar/55.2 kPa). This type of closure minimizes blowing agent losses.

Vented drum closures have been used in the field for over 10 years with no weight loss or significant change in foam density reported.

Note: A smaller  $\frac{3}{4}$  in. solid drum closure is typically used in conjunction with the 2 in. vented drum closure.



# Climate Controlled Storage and Transportation

When formulating spray foam systems using blowing agents and other components, formulators must follow manufacturers' safe use and handling guidelines provided in safety data sheets (SDS) for all ingredients. When handling, storing, and transporting these systems for use in the field, contractors must also carefully adhere to safe use and handling guidelines provided by the formulator, including the use of proper PPE.

## TEMPERATURE CONSIDERATIONS

### Handling and Storage 6

- Adhere to recommended temperature ranges for system components during the blending operation
- Always follow the manufacturer's safe use and handling procedures (refer to Safety Data Sheets) when working with polyol pre-blend
- Climate controlled warehousing may be beneficial
- Store drums on pallets at the recommended temperatures
- Avoid storing in direct sunlight

### Temperature Control


- A cooling blanket 7 on the drum can help prevent internal vapor pressure build-up when the polyol pre-blend may be exposed to high temperatures and/or direct sunlight
- Various cooling blankets options are available from manufacturers, so we recommend exploring a type best suited to your needs and region

### Transportation

- Follow the formulator's instructions for transportation guidance
- During loading and unloading, handle drums with care. Do not drop or roll the drum
- Ensure proper ventilation, such as fans, are used in the work environment, including the rig/trailer
- When possible, refrigerated (air conditioned) trucks/trailers may be beneficial in hot conditions to help maintain desired temperatures and control internal drum vapor pressure
- An alternative method is to apply a cooling blanket over the drum
- Consideration must be given to the time allotted to rest a drum after transport and handling before it is opened, particularly if the drum has been shaken or has been exposed to hot temperatures. With a robust formulation and an adequate resting period, frothing can be reduced and, in some cases, eliminated. This is formulation dependent and results will vary.

### Hot conditions

If the ambient temperature is higher than the recommended temperature for the polyol pre-blend, a number of methods can be employed to help prevent unwanted vapor pressure build-up that can potentially lead to frothing or spouting from the drum.

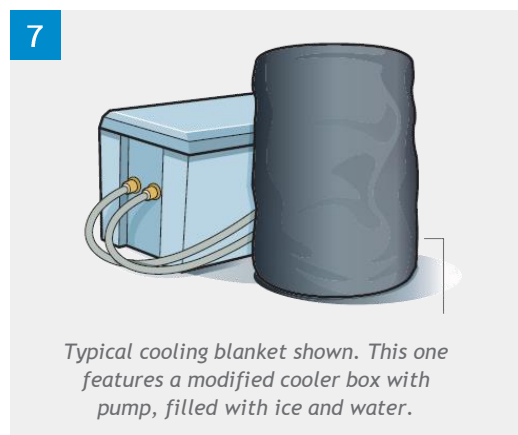

Typical cooling blanket shown. This one features a modified cooler box with pump, filled with ice and water.

While we've presented some of the common methods to help manage internal vapor pressure of drums, Honeywell highly recommends that all schemes to manage vapor pressure be reviewed with the system supplier before implementation.


# Processing Considerations

To maximize performance when spraying a ccSPF system, it is essential that processing parameters for that formulation are carefully followed. Humidity, ambient temperature, and equipment settings are just some of the factors that can impact processing performance. If you are experiencing foam performance issues after carefully following the formulator’s processing recommendations, it may be beneficial to determine whether mechanical factors are contributing.

## Spray foam equipment and components

The choice of spray machine and related components, such as transfer pumps, can directly impact the ease of processing. Different model types are available for contractors. Choosing inadequate or unsuitable components may cause processing issues, such as cavitation or cross-contamination, when spraying the system. Here are some troubleshooting tips to consider that can help prevent and/or address processing-related issues.

SYMPTOMS		POSSIBLE CAUSE(S)		TROUBLESHOOTING TIPS	
1	Off-ratio foam, such as rich MDI or Polyol pre-blend	1a	Screen is clogged at proportioner, causing cavitation	1a	Clean or replace screen
2	Spray pressure fluctuation, such as creeping upward	2a	Ball valve isn't opening completely	2a	Fully open ball valve
		2b	Worn-out seat in ball valve assembly	2b	Replace ball valve
3	Upstroke stalls	3a	Air-cap conical spring failure	3a	Replace spring
		3b	Worn or broken pump packing	3b	Clean or replace pump packing
4	Erratic pump movement	4a	Worn or dirty check valve	4a	Clean or replace check valve
		4b	Loose or separated foot valve	4b	Tighten foot valve

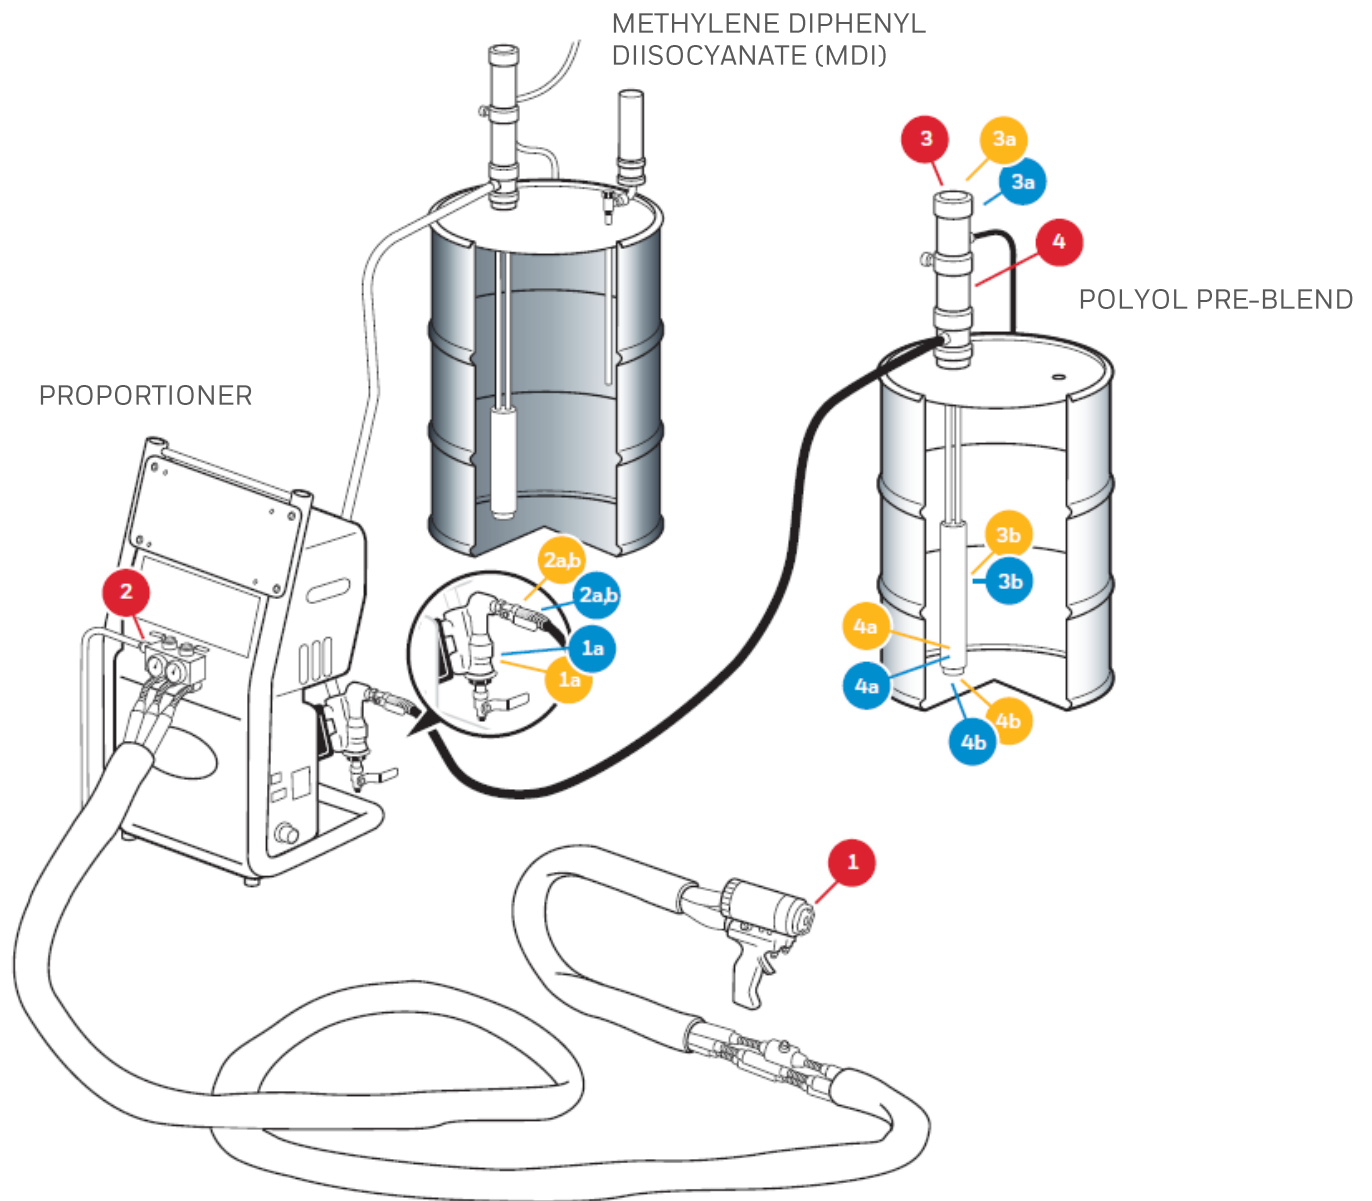

This guide is intended to help address some of the more common factors that can impact polyol pre-blend performance. If your system is still not performing as expected after applying these troubleshooting tips, there are some additional factors that you may want to consider. These include determining whether the system being used is at an elevated temperature, or if the system has been recently agitated. We recognize that every system is unique and factors that can impact its performance are varied. Our Honeywell technical team is ready to assist with your formulation requirements and can discuss additional ways to help you maximize your system's performance.

This is a typical spray foam machine configuration. However, machine configurations may vary. Please check your manufacturer's specifications. Illustration courtesy of Honeywell.



## Worldwide Sales Offices

For more information contact your Honeywell representative.

### United States

Honeywell International  
115 Tabor Road  
Morris Plains, NJ 07950  
Phone: 800-631-8138  
Fax: 973-455-6395

### Latin America/Caribbean

Honeywell Chemicals Mexico  
Constituyentes 900  
Col. Lomas Atlas  
C.P. 950, Mexico DF  
Mexico  
Phone: 52-55-5549-0303  
Fax: 52-55-5544-9803

### Canada

Honeywell Asca. Inc. 3333  
Unity Drive Mississauga,  
Ontario L5L 3S6  
Phone: 905-608-6325  
Fax: 905-608-6327

### Asia-Pacific

Honeywell (China) Co., Ltd.  
No 430, Li Bing Road  
Zhang Jiang Hi-Tech Park  
Pudong New Area, Shanghai  
201203  
China  
Phone: 86-21-2894-2000  
Fax: 86-21-5855-2719

Honeywell Japan Inc.  
New Pier Takeshiba  
South Tower Building, 20th Floor  
1-16-1 Kaigan, Minato-ku,  
Tokyo 050022, Japan  
Phone: 81-3-6730-7000  
Fax: 81-3-6730-7221

Honeywell Chemicals, Korea  
6F Janghakjaedan, B/D 44-1  
Bangpo-Dong, Seocho-Ku  
Seoul 137040, Korea  
Phone: 8-22-595-0204  
Fax: 8-22-595-4964

Honeywell Specialty Chemicals  
(Singapore) Pte. Ltd.  
17 Changi Business  
Park Central 1  
Honeywell Building  
Singapore 486073  
Phone: 65-6355-2828  
Fax: 65-6783-2947

Honeywell Polymers  
(Australia) Pty.  
Limited  
Gr. Lvl. 71 Queens Road  
Melbourne. 3002 Australia  
Phone: 61-3-9529-1411  
Fax: 61-3-9510-9837

**Northern, Central, and  
Eastern Europe, Middle  
East and Africa** Honeywell  
Belgium N.V. Interleuvenlaan  
15i 3001 Heverlee, Belgium  
Phone: 32-16-391-212  
Fax: 32-16-391-371  
E-mail: fluorines.europe@  
honeywell.com

### Southern Europe, Turkey and Israel

Honeywell Fluorine  
Products Italia Srl  
V. Le Milanofiori El  
20090 Assago - MI - Italia  
Phone: 39-02-892589600  
Fax: 39-02-57500815

## Customer Service

To place an order from  
anywhere in the Continental  
United States, Hawaii and  
the Caribbean:

Phone: 800-522-8001  
Fax: 800-458-9073

### Canada

Phone: 800-553-9749  
Fax: 800-553-9750

### Northern and Central Europe

Phone: +32-16-391-209  
Phone: +32-16-391-216  
Fax: +32-16-391-235

### Southern Europe, Middle East and Africa

Phone: +39-02-9379-6777  
ext. 24 / 25 and 26  
Fax: +39-02-9379-6761

### Outside these areas:

Phone: 1-973-455-6300  
Fax: 1-973-455-2763

### For more information

To learn more about the benefits of  
Solstice® Liquid Blowing Agent, visit  
[sustainability.honeywell.com](http://sustainability.honeywell.com)



Although Honeywell International Inc. believes that the information contained herein is accurate and reliable, it is presented without guarantee or responsibility of any kind and does not constitute any representation or warranty of Honeywell International Inc., either expressed or implied. A number of factors may affect the performance of any products used in conjunction with user's materials, such as other raw materials, application, formulation, environmental factors and manufacturing conditions among others, all of which must be taken into account by the user in producing or using the products. The user should not assume that all necessary data for the proper evaluation of these products are contained herein. Information provided herein does not relieve the user from the responsibility of carrying out its own tests and experiments, and the user assumes all risks and liabilities (including, but not limited to, risks relating to results, patent infringement, regulatory compliance and health, safety and environment) related to the use of the products and/or information contained herein.

Solstice is a registered trademark of Honeywell International Inc.  
BA 1734 | February 2022  
© 2022 Honeywell International Inc.

### Honeywell Advanced Materials

115 Tabor Road  
Morris Plains, NJ 07950  
[www.honeywell.com](http://www.honeywell.com)

**THE  
FUTURE  
IS WHAT  
WE  
MAKE IT**

**Honeywell**